



Research Article

Physical and mechanical properties of C class fly ash based lightweight geopolymer mortar produced with expanded vermiculite aggregate

Mehmet Kaya^{1*}, Fuat Köksal²

¹ Department of Civil Engineering, Yozgat Bozok University, Yozgat (Turkey), mehmet.kaya@bozok.edu.tr

² Department of Civil Engineering, Yozgat Bozok University, Yozgat (Turkey), fuat.koksal@bozok.edu.tr

*Correspondence: mehmet.kaya@bozok.edu.tr

Received: 14.08.2021; **Accepted:** 12.12.2021; **Published:** 18.04.2022

Citation: Kaya, M., Köksal, F. (2022). Manuscript title. Revista de la Construcción. Journal of Construction, 21(1), 21-35. <https://doi.org/10.7764/RDLC.21.1.21>.

Abstract: This study presents the physical and the mechanical properties of C class fly ash (FA) based lightweight geopolymer mortars produced with expanded vermiculite (EV) aggregate. The FA was activated with NaOH containing 12%, 14% and 16% sodium by weight. The volumetric ratios of EV/FA in the samples were chosen as 2,4 and 6 in the study. The liquid/solid ratio 0.23, 0.26 and 0.29. Lightweight geopolymer mortar (LGM) samples were produced by mixing FA, EV, NaOH and water in a mixer. The samples placed in molds were exposed to activation temperature of 100°C for 24 hours in the oven. The samples taken out of the oven were demolded and kept in air curing for 28 days at 20°C±2°C room temperature. After curing, unit weight, apparent porosity, water absorption ratio, ultrasonic pulse velocity (UPV), flexural strength and compressive strength tests were performed on the samples. In addition, the thermal conductivity coefficients of the samples were determined. As a result of the experiment, a compressive strength varying between 0.59 MPa and 3.81 MPa was obtained in lightweight geopolymers samples with a unit weight between 906 kg/m³ and 1477 kg/m³. Expanded vermiculite showed a good performance on thermal conductivity of LGMs and a decrease in thermal conductivity up to the 0.094 W/mK was observed.

Keywords: geopolymer, fly ash, vermiculite, flexural strength, compressive strength, thermal conductivity.

1. Introduction

Ordinary Portland Cement (OPC) has the primary binder property with an annual production increase of 9% worldwide (Amran et al. 2020). Annual greenhouse gas emissions from OPC production account for approximately 1.5 billion tons, an average of 6% of total emissions (Castel 2017; Madheswaran, Gnanasundar, and Gopalakrishnan 2013). The concentration of CO₂ in the atmosphere has increased by about 30% recently, reaching 467 Mt. Increasing greenhouse gas levels in the atmosphere cause climate change. As of 2017, total annual greenhouse gas emissions reached a record level, equivalent to 53.5 Gt of CO₂ (UEG 2018). For this reason, many studies are carried out to obtain alternative binders. The main purpose of studies known as geopolymer concrete (Davidovits 2008), alkali activated concrete (Provis 2018) or inorganic concrete (Davidovits 1991) is to produce an eco-friendly binder. Geopolymer helps to reduce resource and energy consumption as well as reducing emissions. Therefore, it can be used as an alternative eco-friendly material (Luo, Xu, and Li 2015). In the production of geopolymer, industrial wastes such as FA, blast furnace slag, silica fume and natural materials such as kaolin, clay, lime

and red mud are used as binders (Bingöl et al. 2020; Khadka et al. 2020; Li et al. 2019; Qu et al. 2020; Sarker 2011; Sukprasert et al. 2021; Yurt 2020a, 2020b). These binders are activated with various alkalis. Alkaline activators such as sodium hydroxide (NaOH) (Atiş et al. 2015; Aygörmez 2021), potassium hydroxide (KOH) (Okoye, Durgaprasad, and Singh 2015; Puligilla, Chen, and Mondal 2019), sodium silicate (Na_2SiO_3) (Yu et al. 2017), potassium silicate (K_2SiO_3) (Chi et al. 2019) are used in the activation process. These activators can be used alone or as a mixture of NaOH + Na_2SiO_3 and KOH+ K_2SiO_3 (Hosan, Haque, and Shaikh 2016; Kaya et al. 2018). A temperature of 300°C is needed for the production of sodium hydroxide (Onwudili and Williams 2009). Despite these factors, it can be said that geopolymer is more economical and more environmentally friendly compared to conventional concrete.

It is quite common to use fossil fuels to meet the energy needs around the world. Some of the electricity need is provided by burning coal in thermal power plants. As a result of the burning of coal, ash is formed both at the base of the combustion unit and in the chimney of the thermal power plant (Yılmaz, et al., 2005). Bottom ash, which is burnt coal waste, and FA from the chimney, has a polluting effect on the environment. However, it causes waste management problems such as storage. It is stated that the FA formed as a result of the burning of coal has reached 750 million tons as of 2015 in the World (Fan et al. 2018). However, currently only 25% are known to be recycled (Gowda and Latha, 2017). Therefore, there is a potential to be used as an alternative to FA OPC. The negative impact on the environment can be eliminated by using OPC and FA in concrete production or using it in geopolymer production (Kaya et al. 2018; Köksal et al. 2015). According to ASTM C618-19 (ASTM 2019), FA, which is obtained from bituminous coal and contains 70% and more $\text{SiO}_2+\text{Al}_2\text{O}_3+\text{Fe}_2\text{O}_3$, is defined as F class. FA, which is obtained from semi-bituminous coal and has more than 50% $\text{SiO}_2+\text{Al}_2\text{O}_3+\text{Fe}_2\text{O}_3$ content, is defined as Class C. It is also stated that CaO ratio is over 10% in C class FA classification.

Vermiculite is a naturally occurring aqueous phyllosilicate mineral (Köksal et al. 2015). It has been reported that vermiculite production in the world is approximately 2.35 million. Major producers of vermiculite are the United States, South Africa, Australia, China, India, Russia, and Uganda (Government of India MoM, 2019). When vermiculite is heated to 650°C-1000°C, it expands to 8-30 times its original volume (Hwang and Hung 2005). Therefore, the expanded form of vermiculite shows very low density, high refractoriness, high sound insulation and low thermal conductivity (Melo et al. 2012; Schackow et al. 2014). In addition, there is no data on the formation of carbon dioxide emissions during the expansion process of vermiculite (Epa U. 1995). Expanded vermiculite is used as aggregate in the production of lightweight concrete due to its lightness, heat and sound insulation properties (Shubbar et al. 2020).

Under ASTM C-332 (ASTM 2017b), LW concrete is 0.7 MPa-2 MPa for insulating concrete applications, and LW concrete is 7 MPa - 14 MPa for masonry applications under ASTM C-331 (ASTM 2017a). In structural applications, LW concrete is within the scope of ASTM C-330 (ASTM 2017c) as 17 MPa - 63 MPa. There are many studies on cement based materials produced with lightweight aggregates such as expanded polystyrene, pumice, perlite and expanded clay (Demirboğa and Gül 2003; Schackow et al. 2014; Sengul et al. 2011). However, studies done by using cementitious materials and expanded vermiculite are limited (Köksal et al. 2015; Mo et al. 2018; Shoukry et al. 2016).

There are many studies in production of geopolymer using different aggregates. Hajimohammadi et al. (2019) examined the interface chemistry in geopolymers containing fly ash. They stated that the compressive strength increased by 30% as a result of the displacement of sand and glass aggregate in the composite. Gowda and Latha (Gowda and Latha 2017) obtained a compressive strength of 6 MPa - 70 MPa at the end of 28 days in the granulated blast furnace slag based geopolymers where they used fine and coarse aggregates. In a study that produced geopolymer using expanded clay aggregate, it was found that the use of 75% expanded clay aggregate reduced the compressive strength from 69 MPa to 10.9 MPa (Hassan et al. 2019). Safari et al. (2020) reported that compressive strength decreased from 76.73 MPa to 64.28 MPa by increasing the curing temperature from 60°C to 80°C during the production of pumice powder-based geopolymer pastes. In a study where fly ash based geopolymer was produced using pumice and expanded perlite as aggregates, a strength between 10 MPa and 50 MPa was obtained (Top et al. 2020). Wongsu et al. (2018), obtained a compressive strength of 8.2 MPa–18.3 MPa and a density of 1685 kg/m³–1749 kg/m³ in geopolymer concretes produced using crushed clay brick and pumice aggregate. In a study where geopolymer was produced with vermiculite aggregate, density between 700 kg/m³ and 900 kg/m³, an average strength of 2 MPa and a thermal conductivity of 0.2 W/mK were determined (Medri et al. 2015). Gencil et al. (2021) produced fly ash

based geopolymer by replacing natural sand and vermiculite aggregate. They stated that with the increase of expanded vermiculite from 15% to 30%, the viscosity decreased approximately 4%, dry unit weight 6%, compressive strength 7%, UPV 6%, thermal conductivity 18%, water absorption 9% and porosity increased 6%.

Studies using expanded vermiculite in geopolymer production are extremely limited in the literature. In this study, fly ash, which is industrial waste as binder, and expanded vermiculite as lightweight aggregate, were used and LGM was produced. The physical and mechanical properties of these composites were investigated.

2. Materials and methods

2.1. Materials

Class C (high-calcium) fly ash, provided from Soma thermal power plant in Turkey was used in this study. The chemical content and physical properties of fly ash are given in Table 1. The scanning electron microscope (SEM) image is also given in Figure 1. Commercially available expanded vermiculite (EV) with a grain size of 0-4 mm was used as lightweight aggregate. The picture and SEM image of EV were presented in Figure 2 and Figure 3, respectively. Some characteristics and chemical properties of expanded vermiculite used were also given in Table 2 and Table 3, respectively. NaOH was used as activator in production of LGM.

Table 1. Properties of C Class fly ash.

Properties	(%)
chemical composition	
MgO	0.62
Al ₂ O ₃	6.36
SiO ₂	15.04
SO ₃	6.92
Na ₂ O	0.06
K ₂ O	0.7
CaO	51.22
Fe ₂ O ₃	2.29
P ₂ O ₅	0.10
LOI	16.62
Physical properties	
Specific weight (t/m ³)	2.68
45 micron sieve remaining (%)	9.1
Blain specific surface (cm ² /g)	2460

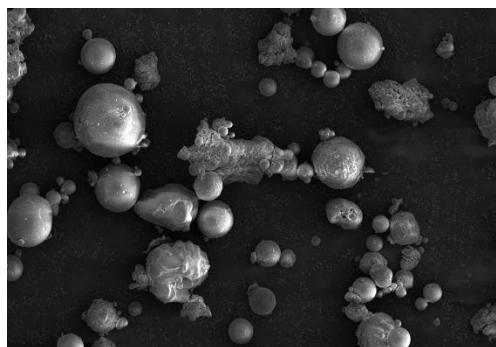


Figure 1. SEM image of class C fly ash.



Figure 2. Expanded vermiculite used.

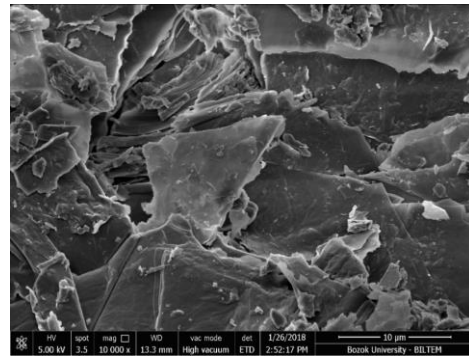


Figure 3. SEM image of expanded vermiculite.

Table 2. Some characteristics of expanded vermiculite used.

Color	Golden
Shape	Accordion shaped granule
Water holding capacity	220% (by weight) 24% (by volume)
Cation exchange capacity	50-150 meg/100 g
Thermal conductivity	0.065-0.062 W/m.K
Permeability	95%
pH	8.1
Sintering temperature	1150 °C-1250 °C
Combustibility	Non-combustible
Specific heat	0.20–0.26 Kcal/kg °C
Specific gravity	2.6
Bulk density	147 kg/m ³

Table 3. Chemical composition of expanded vermiculite used.

Composition	(%)
BaSO ₄	-
SiO ₂	38.76
Al ₂ O ₃	15.89
Fe ₂ O ₃	12.06
CaO	2.32
SO ₃	0.38
MgO	17.69
Na ₂ O	0.30
K ₂ O	5.50
SrSO ₄	-
MnO	-
Loss on ignition	4.86

2.2 Method

In this study, fly ash was activated with NaOH containing 12%, 14% and 16% Na by weight. Vermiculite used as aggregate was adjusted to be EV/FA 2, 4 and 6 by volume. The liquid/solid ratio in the mixture was determined as 0.23, 0.26 and 0.29. mixing ratios of mortar samples are given in Table 4.

Table 4. Mixing ratio of samples.

Mix No.	Mix code	Na/FA, % (weight)	EV/FA (volume)	Liquid/solid ratio
1	Na12V2-1	12	2	0.23
2	Na12V2-2	12	2	0.26
3	Na12V2-3	12	2	0.29
4	Na14V2-1	14	2	0.23
5	Na14V2-2	14	2	0.26
6	Na14V2-3	14	2	0.29
7	Na16V2-1	16	2	0.23
8	Na16V2-2	16	2	0.26
9	Na16V2-3	16	2	0.29
10	Na12V4-1	12	4	0.23
11	Na12V4-2	12	4	0.26
12	Na12V4-3	12	4	0.29
13	Na14V4-1	14	4	0.23
14	Na14V4-2	14	4	0.26
15	Na14V4-3	14	4	0.29
16	Na16V4-1	16	4	0.23
17	Na16V4-2	16	4	0.26
18	Na16V4-3	16	4	0.29
19	Na12V6-1	12	6	0.23
20	Na12V6-2	12	6	0.26
21	Na12V6-3	12	6	0.29
22	Na14V6-1	14	6	0.23
23	Na14V6-2	14	6	0.26
24	Na14V6-3	14	6	0.29
25	Na16V6-1	16	6	0.23
26	Na16V6-2	16	6	0.26
27	Na16V6-3	16	6	0.29

Samples were coded depending on the Na content, the EV/FA and the liquid/solid ratios. The liquid/solid ratios of 0.23, 0.26 and 0.29 were coded as 1, 2 and 3, respectively. For instance, Na12V4-2 mix code refers the mixture with 12% Na content where EV/FA and the liquid/solid ratios are 4 and 0.26. LGM samples were prepared by mixing FA, NaOH, EV and water in a standard cement mixer. The prepared fresh mortars were placed in 40×40×160 mm³ sized 3-cavity molds and disc molds with a diameter of 250 mm and a thickness 20 mm. After placing molds, they were placed in an oven and were kept in there for 24 hours at 100°C activation temperature. After that, they were taken out of the oven and were kept in air curing at 22±2 °C room temperature for up to 28 days. Physical properties of LGMs such as unit weight, apparent porosity, water absorption ratio, UPV and thermal conductivity were determined at the end of 28 days. UPV test was made in accordance with TS EN 12504-4 standard (Turkish Standard Institution 2004). Flexural and compressive strength tests were also made according to TS EN 1015-11 standard (Turkish Standard Institution 2019). Tests for physical properties and strengths were carried out on prismatic mortar samples. Thermal conductivity test was performed on plate disc samples.

3. Experimental results and analysis

3.1. Dry unit weight

Dry unit weights of the samples are given in Figure 4. Unit weights of LWG samples vary between 906 kg/m³ and 1477 kg/m³. The average unit weights of the samples with the EV/FA volumetric ratio of 2, 4, 6 were determined as 1280 kg/m³, 1122 kg/m³ and 1045 kg/m³, respectively.

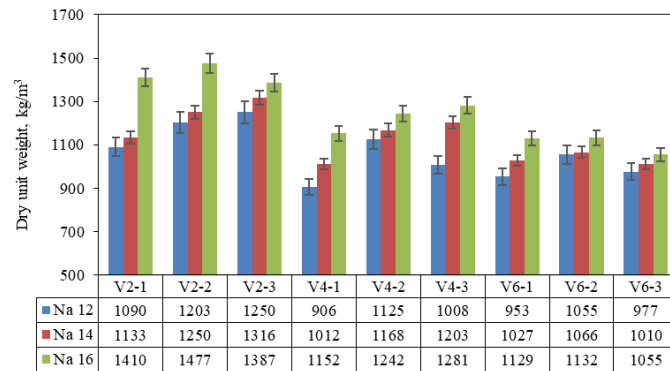


Figure 4. Dry unit weights of the samples.

With the increase in the amount of EV in the mixtures, a decrease in the unit weights was observed. Since the density of EV is less than the density of FA, a decrease in unit weights has been observed with the increase in the amount of EV in the mixture. Unit weights increased with the increase of Na content in the mixtures. It is stated that unit weights increase with the increase of activator ratio in geopolymer mortars containing fly ash (Atabey et al. 2020; Çelikten 2021; Kaya and Köksal 2021). The increase in the activator ratio increases the condensation and consolidation between the particles (Görhan and Kürklü, 2014). In a study where foam concrete was produced using vermiculite, cement and silica fume, it was stated that the unit weights varied between 587 kg/m³-1040 kg/m³ (Köksal, Sahin, and Gencel 2020). In another study where fly ash-based geopolymer was produced using pumice and expanded perlite as aggregates, the lowest unit weight was found to be 1250 kg/m³ (Top et al. 2020).

3.2. Apparent porosity and water absorption ratio

The apparent porosity and water absorption ratios of the LWG samples are given in Figure 5 and Figure 6, respectively. The porosities of the samples vary between 11.55% and 27.27%, and the water absorption ratios vary between 4.88% and 24.66%. The lowest porosity and water absorption ratio were obtained at 2% EV/FA where Na was 16% and liquid/solid ratio was 0.23. The highest porosity and water absorption ratio were determined in samples with a EV/FA ratio of 6, liquid/solid ratio of 0.23 produced with 12% Na. For samples with EV/FA ratios of 2, 4 and 6, the average apparent porosity was 17%, 21.47%, 23.07%, and water absorption ratios were 12%, 18.14%, 19.81%, respectively. With the increase in EV/FA ratio, an increase was observed in water absorption and apparent porosity as a result of high porous structure of expanded vermiculite. As the ratio of FA in the mixture decreased with the increase of the EV/FA ratio, the binding property of the particles decreased. For this reason, the porosity has increased in the samples. On the other hand, due to the water retention feature of EV, an increase in the water absorption ratio was observed with the increase in the amount of EV in the samples.

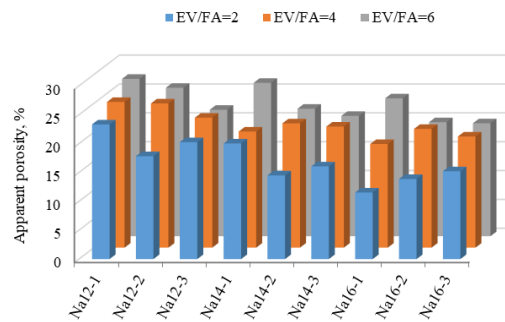


Figure 5. Apparent porosity test results.

The average porosity of the samples containing 12%, 14% and 16% Na were 23.2%, 20.3%, 18.0%, and the water absorption ratios were 19.9%, 16.6% and 13.5%, respectively. The increase in activator ratio increases the concentration and consolidation between particles (Görhan and Kürklü 2014). For this reason, with the increase of Na ratio in the samples, apparent porosity and water absorption ratios decreased. (Tekin et al. 2020) produced geopolymer using zeolitic tuff and marble powder. They found 32% porosity, 22.4% water absorption ratio in samples containing 5 M NaOH (M: concentration of sodium hydroxide in alkaline solution), and 32.8% porosity and 22.3% water absorption ratio in samples containing 10 M NaOH. It has been observed in previous studies that samples produced with high activator concentration have low porosity and water absorption ratios than samples produced with low activator concentration (Aliabdo, et al., 2016; Kaya and Köksal, 2021).

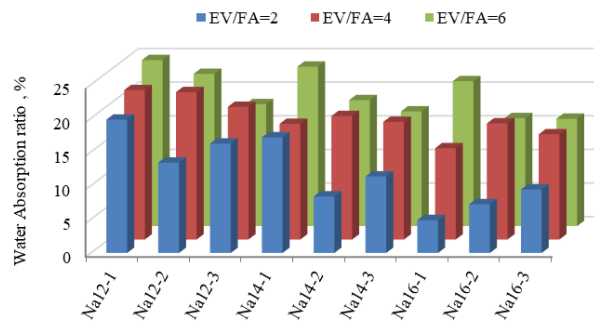


Figure 6. Water absorption ratio test results.

3.3. Ultrasonic pulse velocity (UPV)

UPV values of the LWG samples are given in Figure 7. The UPV of the samples vary between 1296 m/s - 2003 m/s. With the increase in the amount of activator in the samples, the porosity decreased, and consequently, an increase in the UPV was observed. The average UPV values for samples with EV/FA ratio 2, 4 and 6 were determined as 1768 m/s, 1435 m/s and 1384 m/s. With the increase in the amount of vermiculite in the samples, a decrease in the UPV was observed. In a study that produced high calcium fly ash geopolymer using crushed clay bricks and pumice as aggregates, it was detected between 1586 m/s-1858 m/s in pumice aggregated samples (Wongsa et al., 2018). In a study where geopolymer was produced using EV and FA, samples produced with 10 M NaOH showed 3%-11% less UPV ratio compared to samples produced with 15 M NaOH (Tekin et al., 2020). Therefore, the results obtained are consistent with the previous geopolymer studies (Kim et al., 2014). Increasing the activator concentration causes an increase in UPV (Kaya and Köksal 2021; Tekin et al. 2020). UPV is also directly related to the porosity of concrete (Muñoz-Sánchez, Arévalo-Caballero, and Pacheco-Menor 2016).

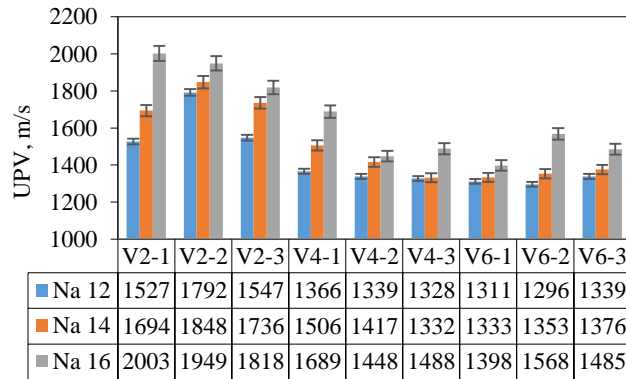


Figure 7. UPV values of the samples.

In a previous study, it was stated that UPV in concrete is significantly affected by aggregate type, unit weight and concrete density (Mohammed and Rahman 2016). In a study where foam concrete was produced using EV and silica fume, UPV values between 1.02 km/s and 1.83 km/s were determined (Koksals et al., 2020). The relationship between the porosity of the samples and the UPV is given in Figure 8. There is a strong correlation with $R^2 = 0.816$ between the porosity and UPV values of the samples. In a study where geopolymer was produced with natural sand and expanded clay aggregate, it was stated that ultrasonic pulse velocities decreased with the increase of clay aggregate (Bhogayata et al., 2020). UPV values increased with the decrease in the void ratio in the samples. The unit weight increases with the decrease in the void ratio in the samples. In a light geopolymer study, there is a $R^2=0.89$ relationship between UPV and unit weight (Wongsa et al., 2018).

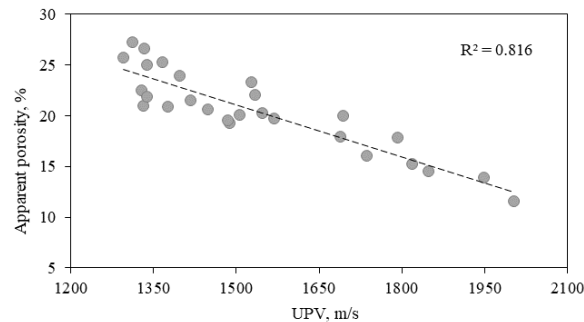


Figure 8. Relationship between apparent porosity and UPV.

3.4 Thermal conductivity

Thermal conductivity values of LGMs were determined by the tests, in which the hot wire method was used, on plate disc samples. The hot wire method is a method based on measuring the temperature rise at a certain distance using a linear heat source (hot wire) embedded in the material to be tested (Davis, 1984). Hot wire method is used to measure and calculate the effective thermal conductivity of granular materials (Gonzo, 2002; Liang and Li, 2006; Tavman, 1996) and building materials (Bouguerra 1999; Bouguerra et al. 1998; Stefanidou et al. 2010). The thermal conductivity test setup and measured values are shown in Figure 9 and Figure 10, respectively.

A significant decrease in thermal conductivity was observed with increasing EV/FA ratio or the amount of EV in the LGM mixture. In a study where foam geopolymer was produced with fly ash, it was stated that the thermal conductivity coefficient decreased with the decrease in density (Shao et al. 2018). In another study where geopolymer was produced with fly ash, a low thermal conductivity up to 0.107 W/mK was detected in the sample with a density of 560 kg/m³ (Novais et al. 2016). In a study where conventional mortar samples were produced using cement and EV, thermal conductivity was found between 0.076-0.105 W/mK (Novais et al. 2016). Al-Si Geopolymer systems have lower thermal conductivity coefficients due to higher void ratios compared to traditional portland cement systems (Pan et al. 2018). In a study where LGW was produced

using EPS (expanded polystyren foam), the presence of EPS led to a significant decrease in thermal conductivity. It was stated that the thermal conductivity reached the highest value in samples with the highest unit weight, while the thermal conductivity was at the lowest value in samples with the smallest unit weight (Colangelo et al. 2018). In foam concretes containing fly ash, the thermal conductivity was reported to be 0.15-0.48 W/mK in samples with densities varying between 585 and 1370 kg/m³ (Zhang et al. 2015). EV is a good thermal insulation material due to its high porosity structure. The reductions in thermal conductivity with addition of EV to LGM mix can be explained as a result of the low thermal conductivity and mineralogical structure of the EV itself. Thermal conductivity values obtained in this experimental study vary between 0.094 W/mK-0.323 W/mK. The lowest thermal conductivity measured as 0.094 W/mK was observed on LGM mixture at which Na content of 12% and EV/FA ratio of 6.



Figure 9. Thermal conductivity test setup.

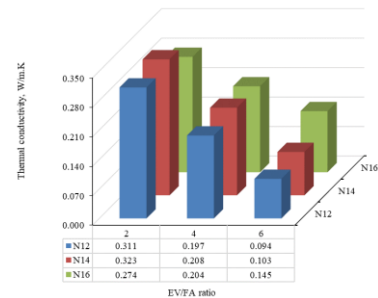


Figure 10. Thermal conductivity test results.

3.5. Flexural strength

Flexural strengths of the LGMs are given in Figure 11. Flexural strength varies between 0.30 MPa and 1.31 MPa. The lowest flexural strength is 0.30 MPa in the sample with an EV/FA ratio of 6 and a liquid/solid ratio of 0.23 produced with 12% Na. The highest flexural strength was determined as 1.31 MPa in the sample with an EV/FA ratio of 2 and a liquid/solid ratio of 0.29 produced with 16% Na. In all samples, an increase in flexural strength was observed with the increase in the activator ratio and the increase in the liquid/solid ratio. The average flexural strengths of the samples with Na ratios of 12%, 14%, 16% were determined as 0.62 MPa, 0.71 MPa and 0.83 MPa, respectively. With the increase of Na ratio from 12% to 16%, the flexural strength increased by 33.8%. Average flexural strengths of samples with a liquid/solid ratio of 2,4,6 were determined as 1.11 MPa, 0.58 MPa and 0.46 MPa, respectively. With the liquid/solid ratio increasing from 2 to 6, the flexural strength decreased by 41.44%. In a study where pumice based geopolymer paste was produced, it was reported that the flexural strength increased at 8 M-12 M NaOH concentration and decreased between 14 M-18 M (Safari et al., 2020). Atiş et al. (Atiş et al. 2015) stated that the flexural strength increases with the increase of Na ratio in fly ash geopolymers that they kept at 105 °C for 24 hours. Kaya and Köksal (2021) stated that the flexural strength of the cement added geopolymer concretes decreased with the increase of the Na/binder ratio. In a study where FA based geopolymer was produced, it was reported that the flexural strength increased by 3.5% with the molarity increasing from 8 to 10 (Mustafa Al Bakri et al., 2012). In another study where geopolymer lightweight concrete was produced with FA, it was stated that the flexural strengths decreased with the decrease of the sample unit weight (Brooks et al., 2010). In this study, unit weights and flexural strengths decreased with the increase of EV/FA ratio as a result of EV's low bulk density as well as low resistance to load. Variation of the flexural strength in the study, depending on the activator ratio, liquid/binder ratio and EV/FA ratio are similar to the literature.

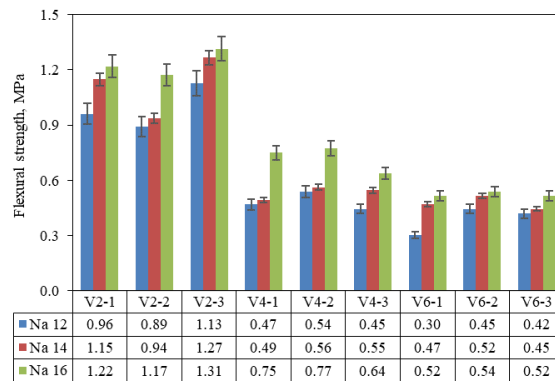


Figure 11. Flexural strength test results.

3.6. Compressive strength

The compressive strengths of the LGM samples are given in Figure 12. Compressive strength varies between 0.59 MPa and 3.81 MPa. The lowest compressive strength is 0.59 MPa in the sample with a EV/FA ratio of 6 and a liquid/solid ratio of 0.23 produced with 12% Na.

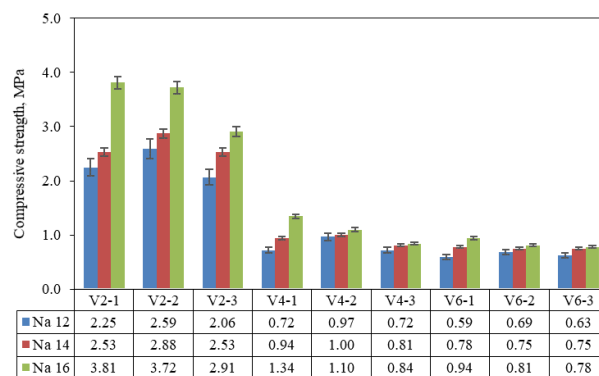


Figure 12. Compressive strength test results.

The highest compressive strength was determined as 3.81 MPa in the sample with an EV/FA ratio of 2 and a liquid/solid ratio of 0.23 produced with 16% Na. In all samples, an increase in compressive strength was observed with the increase in activator ratio and increase in liquid/solid ratio. The average compressive strength of the samples with 12%, 14%, 16% Na ratio was determined as 1.25 MPa, 1.44 MPa and 1.81 MPa, respectively. With the increase of Na ratio from 12% to 16%, the compressive strength increased by 44.8%. Average compressive strengths of samples with liquid/solid ratios of 2, 4, 6 were determined as 2.81 MPa, 0.94 MPa and 0.75 MPa, respectively. With the liquid/solid ratio increasing from 2 to 6, the compressive strength decreased by 73.3%. In a study where lightweight geopolimer panels were produced with vermiculite, the average compressive strength was determined as 2 MPa (Medri et al., 2015). In a study where FA based geopolimer was produced using crushed clay brick and pumice, a strength between 2.7 MPa and 18.3 MPa was obtained. It was stated that the compressive strength values of geopolimers produced with light aggregates decreased compared to samples produced with natural aggregate (Wongsa et al., 2018). As the geopolimer reaction and dissolution increase with the increase of NaOH concentration, an increase in compressive strength is observed (Görhan and Kürklü 2014; Hanjitsuwan et al., 2014; Kaur et al., 2018; Rattanasak and Chindapasirt, 2009). Compressive strengths of LGMs decreased by increasing the amount of EV (or EV/FA ratio) in mixtures. Similar result has been reported by Gencil et al (Gencil et al. 2021). Figure 13. shows the relationship between UPV and compressive strength. There is a relationship between UPV-compressive strength with $R^2=0.847$. Figure 14 shows the relationship between compressive and flexural strength. There is a relationship between compressive strength and flexural strength with $R^2=0.849$. The relationship between UPV and compressive strength is similar to

the literature (Safari et al., 2020). The relationship between flexural strength and compressive strength is similar to FA based geopolymers in the literature (Kaya et al., 2020). In Figure 15, the SEM image of the sample with a EV/FA ratio of 2 and a liquid/solid ratio of 0.29 produced with 12% Na is given after the compressive strength test. The stratified distribution of expanded vermiculite and N-A-S-H gel formation are seen on the Figure 15. In addition, it has been determined that the sample has a gap structure. The layered distribution of expanded vermiculite in the structure and large gaps cause weak bond strength (Tekin et al., 2020).

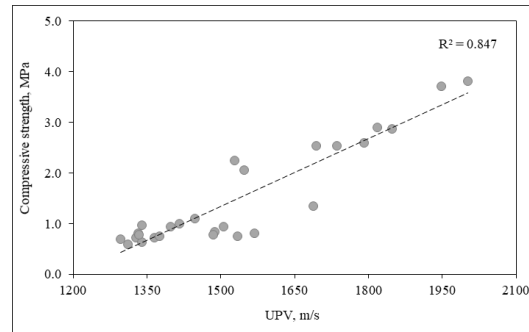


Figure 13. Relationship between UPV and compressive strength.

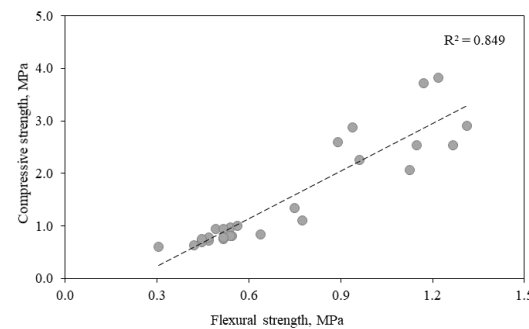


Figure 14. Relationship between flexural and compressive strengths.

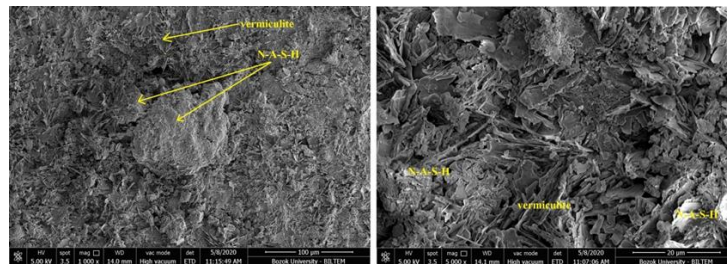


Figure 15. SEM images of LGM coded N12V2-3.

4. Conclusions

In this study, in which vermiculite was used as aggregate in fly ash based LGM, the following results were obtained.

1. Unit weights of LGM samples were determined between 906 kg/m³ and 1477 kg/m³, UPV values between 1296 m/s and 2003 m/s, and flexural strengths between 0.30 MPa and 1.31 MPa.
2. The increase in the amount of activator and liquid/solid ratio increased the reaction of the fly ash in the geopolymer. Thus, geopolymer has a more compact structure. For this reason, water absorption ratio decreased, flexural and compressive strength increased.

3. With the increase of EV/FA ratio, apparent porosity, water absorption ratio increased, but UPV decreased. Pore structure of expanded vermiculite has played very important role on all those properties of LGMs. On the other hand, due to the low strength of expanded vermiculite itself, the flexural and compressive strengths decreased with the increase in the EV/FA ratio. Compressive strength varying between 0.59 MPa and 3.81 MPa was obtained in LGM samples with unit weights varying between 906 kg/m³ and 1477 kg/m³.
4. Improvements were observed in the thermal insulation properties of fly ash based geopolymer mortars with the addition of expanded vermiculite, and LGM with a thermal conductivity of 0.094 W/mK was obtained. So expanded vermiculite could be alternative to other lightweight aggregates such as pumice, expanded clay, etc. for geopolymer insulation material production.

Author contributions: each author contributed to the design and implementation of the research, to the analysis of the results and to the writing of the manuscript.

Funding: none.

Acknowledgments: the author received no financial support for the research, authorship, and/or publication of this article.

Conflicts of interest: the authors declare that they have no conflict of interest.

References

- Aliabdo, Ali A., Abd Elmoaty M. Abd Elmoaty, and Hazem A. Salem. 2016. "Effect of water addition, plasticizer and alkaline solution constitution on fly ash based geopolymer concrete performance." *Construction and Building Materials* 121:694–703. doi: <https://doi.org/10.1016/j.conbuildmat.2016.06.062>.
- Amran, Y. H. Mugahed, Rayed Alyousef, Hisham Alabduljabbar, and Mohamed El-Zeadani. 2020. "Clean production and properties of geopolymer concrete; A review." *Journal of Cleaner Production* 251:119679. doi: <https://doi.org/10.1016/j.jclepro.2019.119679>.
- ASTM. 2017a. "ASTM C330/C330M -17a Standard specification for lightweight aggregates for concrete masonry units."
- ASTM. 2017b. "Standard specification for lightweight aggregates for insulating concrete."
- ASTM. 2017c. Standard specification for lightweight aggregates for structural concrete. ASTM International.
- ASTM, International. 2019. "ASTM C618–19: standard specification for coal fly ash and raw or calcined natural pozzolan for use in concrete." *Annual Book of ASTM Standards* 2019.
- Atabey, İsmail İsa, Okan Karahan, Cahit Bilim, and Cengiz Duran Atis. 2020. "Very high strength Na₂SiO₃ and NaOH activated fly ash based geopolymer mortar."
- Atiş, C. D., E. B. Görür, O. Karahan, C. Bilim, S. İlkentapar, and E. Luga. 2015. "Very high strength (120 MPa) class F fly ash geopolymer mortar activated at different NaOH amount, heat curing temperature and heat curing duration." *Construction and Building Materials* 96. doi: [10.1016/j.conbuildmat.2015.08.089](https://doi.org/10.1016/j.conbuildmat.2015.08.089).
- Aygörmez, Yurdakul. 2021. "Performance of ambient and freezing-thawing cured metazeolite and slag based geopolymer composites against elevated temperatures." *Revista de La Construcción* 20(1). doi: [10.7764/RDLC.20.1.145](https://doi.org/10.7764/RDLC.20.1.145).
- Bhogayata, Ankur, Shemal V Dave, and Narendra K. Arora. 2020. "Utilization of expanded clay aggregates in sustainable lightweight geopolymer concrete." *Journal of Material Cycles and Waste Management* 22(6):1780–92. doi: [10.1007/s10163-020-01066-7](https://doi.org/10.1007/s10163-020-01066-7).
- Bingöl, Şinasi, Cahit Bilim, Cengiz Duran Atiş, Uğur Durak, Serhan İlkentapar, and Okan Karahan. 2020. "An investigation of resistance of sodium meta silicate activated slag mortar to acidic and basic mediums." *Revista de La Construcción*. doi: [10.7764/rdlc.19.1.127-133](https://doi.org/10.7764/rdlc.19.1.127-133).
- Bouguerra, A. 1999. "Temperature and moisture dependence on the thermal conductivity of wood-cement-based composite: experimental and theoretical analysis." *Journal of Physics D: Applied Physics* 32(21):2797.
- Bouguerra, A., A. Ledhem, F. de Barquin, R. M. Dheilly, and M. Quéneudec. 1998. "Effect of microstructure on the mechanical and thermal properties of lightweight concrete prepared from clay, cement, and wood aggregates." *Cement and Concrete Research* 28(8):1179–90. doi: [https://doi.org/10.1016/S0008-8846\(98\)00075-1](https://doi.org/10.1016/S0008-8846(98)00075-1).
- Brooks, Robert, Mozghan Bahadory, Fernando Tovia, and Hossein Rostami. 2010. "Properties of alkali-activated fly ash: high performance to lightweight." *International Journal of Sustainable Engineering* 3(3):211–18. doi: [10.1080/19397038.2010.487162](https://doi.org/10.1080/19397038.2010.487162).

- Castel, A. 2017. "Chapter 14 - Bond between steel reinforcement and geopolymer concrete." Pp. 375–87 in Handbook of Low Carbon Concrete, edited by A. Nazari and J. G. Sanjayan. Butterworth-Heinemann.
- Çelikten, Serhat. 2021. "Mechanical and Microstructural Properties of Waste Andesite Dust-Based Geopolymer Mortars." *Advanced Powder Technology* 32(1):1–9. doi: 10.1016/j.apt.2020.10.011.
- Chi, Hiep Le, Petr Louda, Totka Bakalova, and Vladim\`ir Kovačič. 2019. "Preparation and Mechanical Properties of Potassium Metakaolin Based Geopolymer Paste." *Advanced Engineering Forum* 31:38–45. doi: 10.4028/www.scientific.net/AEF.31.38.
- Colangelo, F., G. Roviello, L. Ricciotti, V. Ferrándiz-Mas, F. Messina, C. Ferone, O. Tarallo, R. Cioffi, and C. R. Cheeseman. 2018. "Mechanical and Thermal Properties of Lightweight Geopolymer Composites." *Cement and Concrete Composites* 86:266–72. doi: <https://doi.org/10.1016/j.cemconcomp.2017.11.016>.
- Davidovits, J. 1991. "Geopolymers: Inorganic Polymeric New Materials." *Journal of Thermal Analysis and Calorimetry* (37):1633–56.
- Davidovits, J. 2008. *Geopolymer Chemistry and Application*. France: institute Geopolymer Saint-Quentin.
- Davis, W. R. 1984. "Hot-Wire Method for the Measurement of the Thermal Conductivity of Refractory Materials." *Compendium of Thermophysical Property Measurement Methods*. 1:231.
- Demirboğa, Ramazan, and Rüstem Gül. 2003. "The Effects of Expanded Perlite Aggregate, Silica Fume and Fly Ash on the Thermal Conductivity of Lightweight Concrete." *Cement and Concrete Research* 33(5):723–27. doi: [https://doi.org/10.1016/S0008-8846\(02\)01032-3](https://doi.org/10.1016/S0008-8846(02)01032-3).
- Epa U. 1995. *AP-42: Compilation of Air Emissions Factors*. Research Triangle Park NC: US Environmental Protection Agency.
- Fan, Fenghong, Zhen Liu, Guoji Xu, Hui Peng, and C. S. Cai. 2018. "Mechanical and Thermal Properties of Fly Ash Based Geopolymers." *Construction and Building Materials* 160:66–81. doi: <https://doi.org/10.1016/j.conbuildmat.2017.11.023>.
- Gencil, Osman, Aliakbar Gholampour, Hayrettin Tokay, and Togay Ozbakkaloglu. 2021. "Replacement of Natural Sand with Expanded Vermiculite in Fly Ash-Based Geopolymer Mortars." *Applied Sciences* 11(4). doi: 10.3390/app11041917.
- Gonzo, Elio E. 2002. "Estimating Correlations for the Effective Thermal Conductivity of Granular Materials." *Chemical Engineering Journal* 90(3):299–302. doi: [https://doi.org/10.1016/S1385-8947\(02\)00121-3](https://doi.org/10.1016/S1385-8947(02)00121-3).
- Görhan, Gökhan, and Gökhan Kürklü. 2014. "The Influence of the NaOH Solution on the Properties of the Fly Ash-Based Geopolymer Mortar Cured at Different Temperatures." *Composites Part B: Engineering* 58:371–77. doi: <https://doi.org/10.1016/j.compositesb.2013.10.082>.
- Government of India MoM. 2019. "Part-III: Mineral Reviews."
- Gowda, S. Prathik, and M. Latha. 2017. "Environmental Concrete-Geopolymer of Construction." *Int. J. Curr. Res* 9:62358–60.
- Hajimohammadi, Ailar, Tuan Ngo, and Jitraporn Vongsvivut. 2019. "Interfacial Chemistry of a Fly Ash Geopolymer and Aggregates." *Journal of Cleaner Production* 231:980–89. doi: <https://doi.org/10.1016/j.jclepro.2019.05.249>.
- Hanjitsuwan, Sakonwan, Sitchai Hunpratub, Prasit Thongbai, Santi Maensiri, Vanchai Sata, and Prinya Chindaprasirt. 2014. "Effects of NaOH Concentrations on Physical and Electrical Properties of High Calcium Fly Ash Geopolymer Paste." *Cement and Concrete Composites* 45:9–14. doi: <https://doi.org/10.1016/j.cemconcomp.2013.09.012>.
- Hassan, Ahmed, Abdel-Hamid I. Mourad, Yasir Rashid, Najif Ismail, and Mohammad Shakeel Laghari. 2019. "Thermal and Structural Performance of Geopolymer Concrete Containing Phase Change Material Encapsulated in Expanded Clay." *Energy and Buildings* 191:72–81. doi: <https://doi.org/10.1016/j.enbuild.2019.03.005>.
- Hosan, Anwar, Sharany Haque, and Faiz Shaikh. 2016. "Compressive Behaviour of Sodium and Potassium Activators Synthesized Fly Ash Geopolymer at Elevated Temperatures: A Comparative Study." *Journal of Building Engineering* 8:123–30. doi: <https://doi.org/10.1016/j.job.2016.10.005>.
- Hwang, Chao-Lung, and Meng-Feng Hung. 2005. "Durability Design and Performance of Self-Consolidating Lightweight Concrete." *Construction and Building Materials* 19(8):619–26. doi: <https://doi.org/10.1016/j.conbuildmat.2005.01.003>.
- Kaur, Mandeep, Jaspal Singh, and Manpreet Kaur. 2018. "Microstructure and Strength Development of Fly Ash-Based Geopolymer Mortar: Role of Nano-Metakaolin." *Construction and Building Materials* 190. doi: 10.1016/j.conbuildmat.2018.09.157.
- Kaya, Mehmet, and Fuat Köksal. 2021. "Effect of Cement Additive on Physical and Mechanical Properties of High Calcium Fly Ash Geopolymer Mortars." *Structural Concrete* 22: E452–E465.
- Kaya, Mehmet, Mucteba Uysal, Kemalettin Yilmaz, and Cengiz Duran Atis. 2018. "Behaviour of Geopolymer Mortars after Exposure to Elevated Temperatures." *Medziagotyra* 24(4). doi: 10.5755/j01.ms.24.4.18829.
- Kaya, Mehmet, Mücteba Uysal, Kemalettin Yilmaz, Okan Karahan, and C. Duran Atis. 2020. "Mechanical Properties of Class C and F Fly Ash Geopolymer Mortars." *Gradjevinar* 72(4). doi: <https://doi.org/10.14256/JCE.2421.2018>.
- Khadka, Suraj D., Priyantha W. Jayawickrama, Sanjaya Senadheera, and Branimir Segvic. 2020. "Stabilization of Highly Expansive Soils Containing Sulfate Using Metakaolin and Fly Ash Based Geopolymer Modified with Lime and Gypsum." *Transportation Geotechnics* 23:100327. doi: <https://doi.org/10.1016/j.trgeo.2020.100327>.

- Kim, Yun Yong, Byung-Jae Lee, Velu Saraswathy, and Seung-Jun Kwon. 2014. "Strength and Durability Performance of Alkali-Activated Rice Husk Ash Geopolymer Mortar." *The Scientific World Journal* 2014.
- Köksal, F., M. A. Serrano-López, M. Şahin, O. Gencil, and C. López-Colina. 2015. "Combined Effect of Steel Fibre and Expanded Vermiculite on Properties of Lightweight Mortar at Elevated Temperatures." *Materials and Structures* 48(7):2083–92. doi: 10.1617/s11527-014-0294-7.
- Köksal, Fuat, Yusa Sahin, and Osman Gencil. 2020. "Influence of Expanded Vermiculite Powder and Silica Fume on Properties of Foam Concretes." *Construction and Building Materials* 257:119547. doi: <https://doi.org/10.1016/j.conbuildmat.2020.119547>.
- Li, Yuancheng, Xiaobo Min, Yong Ke, Degang Liu, and Chongjian Tang. 2019. "Preparation of Red Mud-Based Geopolymer Materials from MSWI Fly Ash and Red Mud by Mechanical Activation." *Waste Management (New York, N.Y.)* 83:202–8. doi: <https://doi.org/10.1016/j.wasman.2018.11.019>.
- Liang, J. Z., and F. H. Li. 2006. "Measurement of Thermal Conductivity of Hollow Glass-Bead-Filled Polypropylene Composites." *Polymer Testing* 25(4):527–31. doi: <https://doi.org/10.1016/j.polymertesting.2006.02.007>.
- Luo, Xin, Jin-yu Xu, and Weimin Li. 2015. "The Preparation of Energy-Absorbing Material by Using Solid Waste." *RSC Adv.* 5(12):9283–89. doi: <https://doi.org/10.1039/C4RA06092J>.
- Madheswaran, C. K., G. Gnanasundar, and N. Gopalakrishnan. 2013. "Effect of Molarity in Geopolymer Concrete." *International Journal of Civil and Structural Engineering* 4:106–15.
- Medri, V., E. Papa, M. Mazzocchi, L. Laghi, M. Morganti, J. Francisoni, and E. Landi. 2015. "Production and Characterization of Lightweight Vermiculite/Geopolymer-Based Panels." *Materials & Design* 85:266–74. doi: <https://doi.org/10.1016/j.matdes.2015.06.145>.
- Melo, Miguel Otávio B. C., Luiz Bueno da Silva, Antonio S. Coutinho, Vivian Sousa, and Normando Perazzo. 2012. "Energy Efficiency in Building Installations Using Thermal Insulating Materials in Northeast Brazil." *Energy and Buildings* 47:35–43. doi: <https://doi.org/10.1016/j.enbuild.2011.11.021>.
- Mo, Kim Hung, Hong Jie Lee, Michael Yong Jing Liu, and Tung-Chai Ling. 2018. "Incorporation of Expanded Vermiculite Lightweight Aggregate in Cement Mortar." *Construction and Building Materials* 179:302–6. doi: <https://doi.org/10.1016/j.conbuildmat.2018.05.219>.
- Mohammed, Tarek Uddin, and Md Nafiur Rahman. 2016. "Effect of Types of Aggregate and Sand-to-Aggregate Volume Ratio on UPV in Concrete." *Construction and Building Materials* 125:832–41. doi: <https://doi.org/10.1016/j.conbuildmat.2016.08.102>.
- Muñoz-Sánchez, Belén, María José Arévalo-Caballero, and María Concepción Pacheco-Menor. 2016. "Influence of Acetic Acid and Calcium Hydroxide Treatments of Rubber Waste on the Properties of Rubberized Mortars." *Materials and Structures* 50(1):75. doi: <https://doi.org/10.1617/s11527-016-0912-7>.
- Mustafa Al Bakri, A. M., H. Kamarudin, M. Bnhussain, A. R. Rafiza, and Yahya Zarina. 2012. "Effect of Na₂ SiO₃/NaOH Ratios and NaOH Molarities on Compressive Strength of Fly-Ash-Based Geopolymer." *ACI Materials Journal* 109(5).
- Novais, Rui M., L. H. Buruberry, G. Ascensão, M. P. Seabra, and J. A. Labrincha. 2016. "Porous Biomass Fly Ash-Based Geopolymers with Tailored Thermal Conductivity." *Journal of Cleaner Production* 119:99–107.
- Okoye, F. N., J. Durgaprasad, and N. B. Singh. 2015. "Fly Ash/Kaolin Based Geopolymer Green Concretes and Their Mechanical Properties." *Data in Brief* 5. doi: <https://doi.org/10.1016/j.dib.2015.10.029>.
- Onwudili, Jude A., and Paul T. Williams. 2009. "Role of Sodium Hydroxide in the Production of Hydrogen Gas from the Hydrothermal Gasification of Biomass." *International Journal of Hydrogen Energy* 34(14):5645–56. doi: <https://doi.org/10.1016/j.ijhydene.2009.05.082>.
- Pan, Zhu, Zhong Tao, Yi-Fang Cao, and Richard Wuhrer. 2018. "Measurement and Prediction of Thermal Properties of Alkali-Activated Fly Ash/Slag Binders at Elevated Temperatures." *Materials and Structures* 51(4):108. doi: <https://doi.org/10.1617/s11527-018-1233-9>.
- Provis, John L. 2018. "Alkali-Activated Materials." *Cement and Concrete Research* 114:40–48. doi: <https://doi.org/10.1016/j.cemconres.2017.02.009>.
- Puligilla, Sravanthi, Xu Chen, and Paramita Mondal. 2019. "Does Synthesized C-S-H Seed Promote Nucleation in Alkali Activated Fly Ash-Slag Geopolymer Binder?" *Materials and Structures* 52(4):65. doi: <https://doi.org/10.1617/s11527-019-1368-3>.
- Qu, Fulin, Wengui Li, Zhong Tao, Arnaud Castel, and Kejin Wang. 2020. "High Temperature Resistance of Fly Ash/GGBFS-Based Geopolymer Mortar with Load-Induced Damage." *Materials and Structures* 53(4):111. doi: <https://doi.org/10.1617/s11527-020-01544-2>.
- Rattanasak, Ubolluk, and Prinya Chindaprasirt. 2009. "Influence of NaOH Solution on the Synthesis of Fly Ash Geopolymer." *Minerals Engineering* 22(12):1073–78. doi: <https://doi.org/10.1016/j.mineng.2009.03.022>.
- Safari, Zrar, Rawaz Kurda, Botan Al-Hadad, Faraydon Mahmood, and Mucip Tapan. 2020. "Mechanical Characteristics of Pumice-Based Geopolymer Paste." *Resources, Conservation and Recycling* 162:105055. doi: <https://doi.org/10.1016/j.resconrec.2020.105055>.
- Sarker, Prabir Kumar. 2011. "Bond Strength of Reinforcing Steel Embedded in Fly Ash-Based Geopolymer Concrete." *Materials and Structures* 44(5):1021–30. doi: <https://doi.org/10.1617/s11527-010-9683-8>.
- Schackow, Adilson, Carmeane Efftig, Marilena V Folgueras, Saulo Güths, and Gabriela A. Mendes. 2014. "Mechanical and Thermal Properties of Lightweight Concretes with Vermiculite and EPS Using Air-Entraining Agent." *Construction and Building Materials* 57:190–97. doi: <https://doi.org/10.1016/j.conbuildmat.2014.02.009>.

- Sengul, Ozkan, Senem Azizi, Filiz Karaosmanoglu, and Mehmet Ali Tasdemir. 2011. "Effect of Expanded Perlite on the Mechanical Properties and Thermal Conductivity of Lightweight Concrete." *Energy and Buildings* 43(2):671–76. doi: <https://doi.org/10.1016/j.enbuild.2010.11.008>.
- Shao, Ning-ning, Yan-bo Zhang, Ze Liu, Dong-min Wang, and Zuo-tai Zhang. 2018. "Fabrication of Hollow Microspheres Filled Fly Ash Based Foam Geopolymers with Ultra-Low Thermal Conductivity and Relative High Strength." *Construction and Building Materials* 185:567–73. doi: <https://doi.org/10.1016/j.conbuildmat.2018.07.077>.
- Shoukry, H., M. F. Kotkata, S. A. Abo-EL-Enein, M. S. Morsy, and S. S. Shebl. 2016. "Enhanced Physical, Mechanical and Microstructural Properties of Lightweight Vermiculite Cement Composites Modified with Nano Metakaolin." *Construction and Building Materials* 112:276–83. doi: <https://doi.org/10.1016/j.conbuildmat.2016.02.209>.
- Shubbar, Ali Abdulhussein, Monower Sadique, Hayder Kamil Shanbara, and Khalid Hashim. 2020. "The Development of a New Low Carbon Binder for Construction as an Alternative to Cement." Pp. 205–13 in *Advances in Sustainable Construction Materials and Geotechnical Engineering*. Springer.
- Stefanidou, Maria, Marc Assael, Konstantinos Antoniadis, and Gregory Matziaroglou. 2010. "Thermal Conductivity of Building Materials Employed in the Preservation of Traditional Structures." *International Journal of Thermophysics* 31(4):844–51. doi: <https://doi.org/10.1007/s10765-010-0750-8>.
- Sukprasert, Sart, Menglim Hoy, Suksun Horpibulsuk, Arul Arulrajah, Ahmad Safuan A. Rashid, and Ramli Nazir. 2021. "Fly Ash Based Geopolymer Stabilisation of Silty Clay/Blast Furnace Slag for Subgrade Applications." *Road Materials and Pavement Design* 22(2):357–71. doi: <https://doi.org/10.1080/14680629.2019.1621190>.
- Tavman, I. H. 1996. "Effective Thermal Conductivity of Granular Porous Materials." *International Communications in Heat and Mass Transfer* 23(2):169–76. doi: [https://doi.org/10.1016/0735-1933\(96\)00003-6](https://doi.org/10.1016/0735-1933(96)00003-6).
- Tekin, Ilker, Osman Gencel, Aliakbar Gholampour, Osman Hulusi Oren, Fuat Koksak, and Togay Ozbakkaloglu. 2020. "Recycling Zeolitic Tuff and Marble Waste in the Production of Eco-Friendly Geopolymer Concretes." *Journal of Cleaner Production* 268:122298. doi: <https://doi.org/10.1016/j.jclepro.2020.122298>.
- Top, Soner, Hüseyin Vapur, Mahmut Altiner, Dogan Kaya, and Ahmet Ekicibil. 2020. "Properties of Fly Ash-Based Lightweight Geopolymer Concrete Prepared Using Pumice and Expanded Perlite as Aggregates." *Journal of Molecular Structure* 1202:127236. doi: <https://doi.org/10.1016/j.molstruc.2019.127236>.
- Turkish Standard Institution. 2004. "12504-4. Testing Concrete–Part 4: Determination of Ultrasonic Pulse Velocity." 18.
- Turkish Standard Institution. 2019. "Methods of Test for Mortar for Masonry-Part 11: Determination of Flexural and Compressive Strength of Hardened Mortar."
- UEG, Report. 2018. "No Title." Retrieved (<https://wedocs.unep.org/bitstream/handle/20.500.11822/34438/EGR20ESE.pdf?sequence=25>).
- Wongsa, Ampol, Vanchai Sata, Peem Nuaklong, and Prinya Chindaprasirt. 2018. "Use of Crushed Clay Brick and Pumice Aggregates in Lightweight Geopolymer Concrete." *Construction and Building Materials* 188:1025–34. doi: <https://doi.org/10.1016/j.conbuildmat.2018.08.176>.
- Yılmaz B Erdoğan, E. Erdoğan Y. 2005. "Investigation of the Effect of Sodium Carbonate Addition on Fly Ash Base Ash and Cements with Wallstonite." in *Symposium on Chemical Additives in Buildings*. Chamber of civil engineers.
- Yu, Xiao, Linhua Jiang, Jinxia Xu, and Yuheng Zu. 2017. "Effect of Na₂SiO₃ Content on Passivation and Corrosion Behaviour of Steel in a Simulated Pore Solution of Na₂SiO₃-Activated Slag." *Construction and Building Materials* 146:156–64. doi: <https://doi.org/10.1016/j.conbuildmat.2017.04.091>.
- Yurt, Ümit. 2020a. "An Experimental Study on Fracture Energy of Alkali Activated Slag Composites Incorporated Different Fibers." *Journal of Building Engineering* 32:101519. doi: <https://doi.org/10.1016/j.job.2020.101519>.
- Yurt, Ümit. 2020b. "High Performance Cementless Composites from Alkali Activated GGBFS." *Construction and Building Materials* 264:120222. doi: <https://doi.org/10.1016/j.conbuildmat.2020.120222>.
- Zhang, Zuhua, John L. Provis, Andrew Reid, and Hao Wang. 2015. "Mechanical, Thermal Insulation, Thermal Resistance and Acoustic Absorption Properties of Geopolymer Foam Concrete." *Cement and Concrete Composites* 62:97–105. doi: <https://doi.org/10.1016/j.cemconcomp.2015.03.013>.



Copyright (c) 2022. Kaya, M., Köksal, F. This work is licensed under a [Creative Commons Attribution-Noncommercial-No Derivatives 4.0 International License](https://creativecommons.org/licenses/by-nc-nd/4.0/).